

# Diode-Pumped Passively Mode-Locked Nd:YVO<sub>4</sub> Lasers With 40-GHz Repetition Rate

Steve Lecomte, Markus Kalisch, Lukas Krainer, Gabriel J. Spühler, Rüdiger Paschotta, Matthias Golling, Dirk Ebling, Tsuyoshi Ohgoh, Toshiro Hayakawa, *Senior Member, IEEE*, Susanne Pawlik, Berthold Schmidt, *Member, IEEE*, and Ursula Keller, *Senior Member, IEEE*

**Abstract**—We present two different diode-pumped passively mode-locked Nd:YVO<sub>4</sub> lasers with a repetition rate of 40 GHz. This is the highest repetition rate demonstrated so far with diode-pumped 1- $\mu\text{m}$  solid-state lasers. The first laser design allows short pulses of 2.7-ps duration whereas the second laser design is optimized for high average output power of up to 288 mW. We compare both design approaches and show that there is a tradeoff between output power and pulse duration.

**Index Terms**—Diode-pumped lasers, high-pulse repetition rates, mode-locked lasers, semiconductor absorbers.

## I. INTRODUCTION

PROGRESS over the last decade in ultrafast all-solid-state lasers has pushed performance in average power and pulse repetition rate by 2–3 orders of magnitude [1]. Trains of picosecond or femtosecond mode-locked pulses at repetition rates of several gigahertz are required for various applications like telecommunications [2], optical clocking of very fast computer processors [3], high-speed electro-optic sampling [4], analog-to-digital conversion, time-resolved spectroscopy with high signal-to-noise ratio [5], generation of polarized electron beams for particle accelerators [6], and pumping of optical parametric oscillators [7], [8]. Such pulse trains should be generated with compact, efficient and reliable lasers delivering at least a few picojoules of pulse energy (e.g., 1 pJ of pulse energy with a pulse repetition rate of 40 GHz corresponds to an average output power of 40 mW). The noise properties are also very important, and timing stabilization of the laser using an external microwave reference oscillator may be required [9]. Depending on the application, the emission wavelength can be of concern and might ideally be tunable. For example,

Manuscript received July 8, 2004; revised August 25, 2004. This work was supported in part by the Swiss Innovation Promotion Agency KTI/CTI (Commission for Technology and Innovation).

S. Lecomte, M. Kalisch, L. Krainer, G. J. Spühler, R. Paschotta, M. Golling, and U. Keller are with the Institute of Quantum Electronics, Physics Department, Swiss Federal Institute of Technology (ETH), ETH Zürich Hönggerberg, CH-8093 Zürich, Switzerland (e-mail: lecomte@phys.ethz.ch; krainer@phys.ethz.ch; spuehler@phys.ethz.ch; paschotta@phys.ethz.ch; golling@phys.ethz.ch; keller@phys.ethz.ch).

D. Ebling is with the FIRST Center for Micro- and Nanoscience, Swiss Federal Institute of Technology (ETH), ETH Zürich Hönggerberg, CH-8093 Zürich, Switzerland (e-mail: ebling@first.ethz.ch).

T. Ohgoh and T. Hayakawa are with Advanced Core Technology Laboratories, Fuji Photo Film Co., Ltd., Miyanodai Technology Development Center, Kanagawa 258-8538, Japan (e-mail: haya@miya.fujifilm.co.jp).

S. Pawlik and B. Schmidt are with Bookham (Switzerland) AG, CH-8045 Zürich, Switzerland (e-mail: susanne.pawlik@bookham.com; berthold.schmidt@bookham.com).

Digital Object Identifier 10.1109/JQE.2004.838532

for telecommunication through optical fibers, the often used *C*-band has a wavelength region between 1530 and 1565 nm. Optical parametric oscillators allow coverage of even much wider wavelength ranges [8]; for multigigahertz pulse repetition rates, they require solid-state pump lasers with optimized output power.

Several approaches are currently being explored to generate mode-locked pulses at gigahertz repetition rates. One common approach is represented by actively and passively mode-locked fiber lasers. These lasers can produce very high repetition rates of up to 200 GHz [10] but at the cost of a high complexity due to harmonic mode locking and relatively low output powers of at most a few tens of milliwatts. Even higher repetition rates of more than 1 THz can be reached with mode-locked edge-emitting semiconductor lasers [11]. In general, the pulses from such laser diodes are strongly chirped, and the average output power is typically only a few milliwatts or even below 1 mW. Optically pumped vertical-external cavity surface-emitting semiconductor lasers (VECSELs) that are passively mode-locked with a semiconductor saturable absorber (SESAM) [12], [13], can generate high average output powers in picosecond pulses of good quality [14], [15], and close to transform-limited femtosecond pulses [16]. Recently, a 10-GHz device of this kind with 1.4 W average output power has been demonstrated [17], and higher repetition rates should be possible.

Here we present another class of lasers based on a Nd:YVO<sub>4</sub> crystal and on passive mode locking using a SESAM. This concept has been demonstrated with up to a 157-GHz repetition rate [18], but so far repetition rates higher than 13 GHz [19] have required the use of a Ti:sapphire laser as a pump source with high brightness. A 10-GHz diode-pumped laser was optimized for a high average output power of 2.1 W [18]. Table I presents a summary of 1- $\mu\text{m}$  solid-state lasers with repetition rates above 1 GHz. Similar lasers with Er:Yb:glass as gain medium, emitting within the telecom *C*-band, have been demonstrated with repetition rates of up to 50 GHz [20]. Both types of lasers produced pulses of some picosecond durations and of very high quality.

In this paper, we present diode-pumped passively mode-locked Nd:YVO<sub>4</sub> lasers with repetition rates around 40 GHz. This is the highest repetition rate achieved so far for diode-pumped 1- $\mu\text{m}$  lasers (see Table I). A key point was the use of novel high-brightness pump diodes. We demonstrate two different laser designs meeting different goals. In Section II, we describe a laser optimized for short pulses of 2.7-ps duration with an average output power of 49 mW, whereas in Section III we present a second laser producing longer pulses with 6.5-ps

TABLE I  
1- $\mu\text{m}$  SOLID-STATE LASERS WITH REPETITION RATES ABOVE 1 GHz

Laser Material	ML technique	$\lambda_0$	$\tau_p$	$P_{\text{av, out}}$	$f_{\text{rep}}$	Pumping	Ref.
Nd:YLF	Active AOM	1.047 $\mu\text{m}$	7 ps	135 mW	2 GHz	Diode pumped	[21]
Nd:YLF	Active EOM	1.053 $\mu\text{m}$	4.5 ps	400 mW	2.85 GHz	Diode pumped	[22]
Nd:YLF	Active EOM	1.053 $\mu\text{m}$	13 ps	350 mW	5 GHz	Ti:sapphire laser pumped	[23]
Nd:BEL	Active EOM	1.070 $\mu\text{m}$	3.9 ps	30 mW	20 GHz	Diode pumped	[24]
Nd:GdVO <sub>4</sub>	Passive SESAM	1.063 $\mu\text{m}$	12 ps	500 mW	10 GHz	Diode pumped	[9]
Nd:YVO <sub>4</sub>	Passive SESAM	1.064 $\mu\text{m}$	14 ps	2100 mW	10 GHz	Diode pumped	[18]
Nd:YVO <sub>4</sub>	Passive SESAM	1.064 $\mu\text{m}$	8.3 ps	198 mW	13 GHz	Diode pumped	[19]
Nd:YVO <sub>4</sub>	Passive SESAM	1.064 $\mu\text{m}$	$\approx$ 5.3 ps	$\approx$ 60 mW	39, 49, 59 GHz	Ti:sapphire laser pumped	[25]
Nd:YVO <sub>4</sub>	Passive SESAM	1.064 $\mu\text{m}$	2.7 ps	$\approx$ 50 mW	77, 157 GHz	Ti:sapphire laser pumped	[26, 18]
Nd:YVO <sub>4</sub>	Passive SESAM	1.064 $\mu\text{m}$	6.5 ps	288 mW	40 GHz	Diode pumped	This publication
Nd:YVO <sub>4</sub>	Passive SESAM	1.064 $\mu\text{m}$	2.7 ps	49 mW	39 GHz	Diode pumped	This publication

ML technique: mode-locking technique.  $\lambda_0$ : center lasing wavelength.  $\tau_p$ : measured pulse duration.  $P_{\text{av, out}}$ : average output power.  $f_{\text{rep}}$ : pulse repetition rate. AOM: acousto-optic modulator. EOM: electro-optic phase modulator. SESAM: semiconductor saturable absorber mirror.

duration but at a much higher average output power of 288 mW. We compare both approaches and discuss a tradeoff between output power and pulse duration.

## II. 39-GHz Nd:YVO<sub>4</sub> LASER FOR SHORT PULSES

### A. Concept and Previous State of the Art

Passively mode-locked Nd:YVO<sub>4</sub> lasers pumped with Ti:sapphire lasers have already been demonstrated with repetition rates up to 157 GHz [18]. The laser with a 157-GHz repetition rate emitted 2.7-ps pulses with 45 mW of average output power for 500 mW of pump power. A laser of the same type with a repetition rate of 39 GHz emitted longer pulses of 5.5 ps with 60 mW of average output power [25]. In both cases, a quasi-monolithic laser design was used where basically the whole intracavity path length is within the Nd:YVO<sub>4</sub> crystal (see Fig. 1). The crystal thickness is, e.g., 1.74 mm for the 39-GHz laser presented here, or 0.44 mm for the 157-GHz laser. One crystal facet, which acts as the output coupler, is curved and dielectrically coated. The other facet is flat, polished and can be antireflection coated or uncoated. The SESAM is mounted close to the flat crystal facet with an air gap of a few micrometers thickness between crystal and SESAM. For fine adjustment of the air gap, the SESAM is mounted on a piezoelectric transducer. To suppress  $Q$ -switching instabilities [27] for the typical intracavity powers of such lasers, the laser mode radius in the gain medium has to be in the order of 20  $\mu\text{m}$ . This is achieved e.g., with a radius of curvature of the crystal facet of 10 mm for a 40-GHz laser.

Because this kind of laser has to be operated very far above the pump threshold in order to suppress  $Q$ -switching instabilities, great care has to be taken to avoid the excitation of higher-order transverse cavity modes, which would destabilize the mode-locking process. Therefore, the pump beam radius should be at most about 3/4 of the laser beam radius over the whole crystal length. (Even after a propagation length corresponding to several pump absorption lengths, a larger pump beam radius is not acceptable.) As a consequence, the pump beam quality factor  $M^2$  must be smaller than  $\approx 2$ , while  $\approx 300$  mW of power is required. Until recently, the resulting high pump brightness could be achieved only by using a Ti:sapphire pump laser, but in the meantime, semiconductor diode lasers with sufficient brightness have been developed.

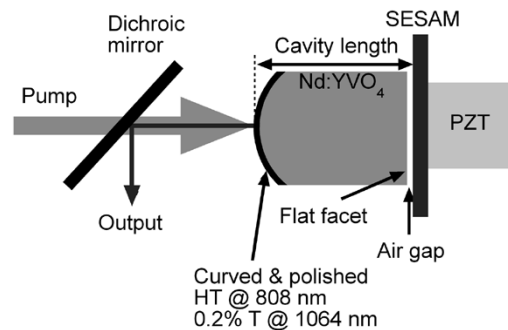


Fig. 1. Laser setup of the 39-GHz laser optimized for short pulses. The pump and laser beam are separated with a dichroic mirror. PZT stands for piezoelectric transducer.

### B. Experimental Setup

Our pump diode is a single-mode AlGaAs–GaAs device provided by Bookham (Switzerland) AG. It can emit up to 500 mW in a close to diffraction-limited beam ( $M^2 < 1.3$ ). To avoid catastrophic damage, we run the diode with 400 mA, obtaining 379 mW incident on the Nd:YVO<sub>4</sub> crystal. Due to the E2-facet passivation technology [28], this single-mode laser reveals an excellent reliability at high-power densities. For a mount temperature of 24 °C, the optical spectrum is centered at 808.7 nm and has a spectral linewidth below 1 nm. The slightly asymmetric beam of the diode was shaped to a nearly circular beam at the laser crystal using two cylindrical lenses. Using an achromatic lens with 35-mm focal length, we obtained a beam radius in the laser crystal of  $\approx 17$   $\mu\text{m}$ .

We used a Nd:YVO<sub>4</sub> crystal with 3% neodymium doping. This doping level might appear to be higher than necessary for good pump absorption, but it reduces the sensitivity to the pump wavelength and bandwidth without introducing thermal problems at this power level. The curved side of the crystal was polished with a radius of 10 mm. It was coated for high transmission at the pump wavelength and  $\approx 0.2\%$  transmission at the laser wavelength. The flat facet remained uncoated. This aspect is important and will be discussed below. The SESAM is similar to the one used in the 157-GHz laser [18]. It consists of a high-reflecting AlAs–GaAs Bragg mirror followed by a single InGaAs quantum well absorber in an antiresonant structure. Three Bragg pairs of AlAs–GaAs were deposited on the top of the structure to reduce the nonsaturable losses to less than 0.1% at the expense

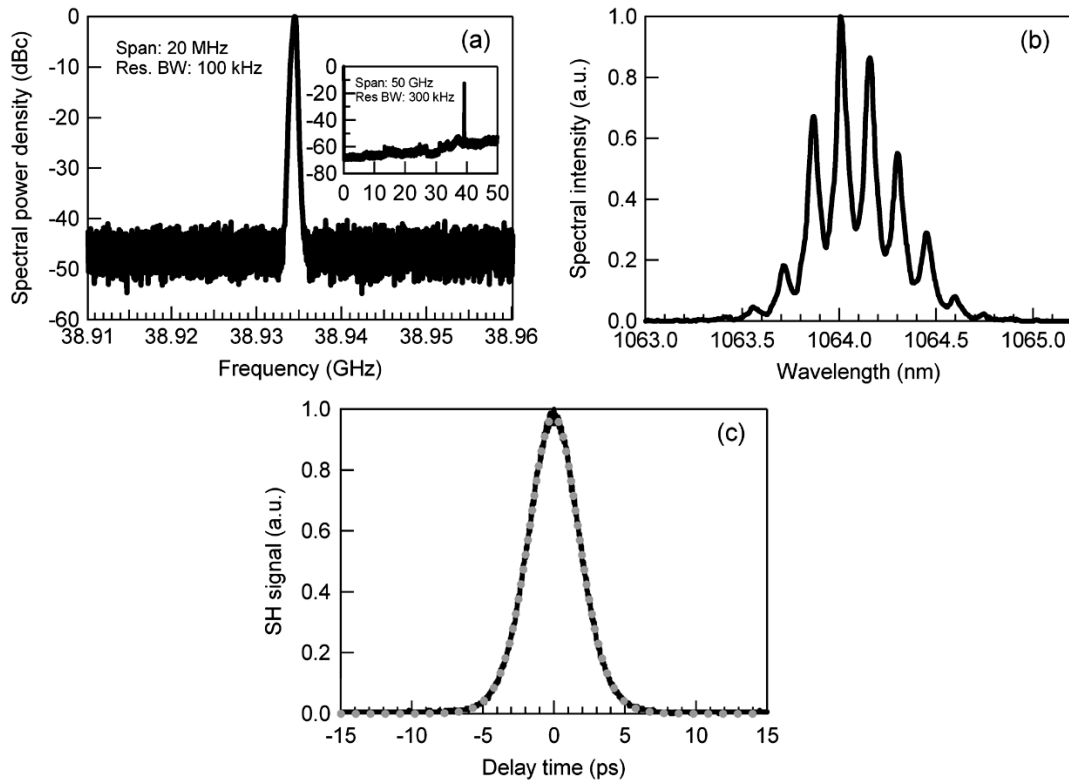


Fig. 2. (a) Radio frequency spectra of the 39-GHz short pulse laser, showing stable mode locking. (b) Optical spectrum measured with 0.08 nm resolution bandwidth. The longitudinal modes with 39-GHz spacing are partly resolved. (c) Autocorrelation trace. The  $\text{sech}^2$  fit (dots) fully overlaps with the autocorrelation trace (line). The pulse length is 2.7 ps.

of a lower modulation depth of 0.3% and a higher saturation fluence of  $60 \mu\text{J}/\text{cm}^2$ . The absorber recovery time is 28 ps.

### C. Experimental Results

With 379 mW of pump power, the laser produced 49 mW of output power at a repetition rate of 38.9 GHz. The pulse energy was 1.3 pJ. The laser operated on a single transverse mode with  $M^2 < 1.15$ . The relaxation oscillations are firmly suppressed as shown in the RF spectrum [Fig. 2(a)]. The optical spectrum [Fig. 2(b)] has a linewidth of about 0.35 nm. The autocorrelation [Fig. 2(c)] is well fitted for  $\text{sech}^2$ -shaped pulses and indicates a pulse length of 2.7-ps, which agrees with the transform limit for the measured optical spectrum.

### D. Effect of the Air Gap Between Crystal and SESAM

While the previous 39-GHz laser [25] had an antireflection coating on the flat side of the crystal, the laser described here has an uncoated flat side. Due to the strong Fresnel reflection of this surface and the air gap between the crystal and the SESAM, we effectively have a Fabry–Perot resonator. When the resonance condition of this Fabry–Perot resonator is tuned with the piezo below the SESAM, the pulse duration, pulse stability and output power change with a  $\lambda/2$  period. Stable pulses with the shortest duration of 2.7 ps are reached when the average power has its maximum. This observation first appeared to be rather surprising, because one should expect the strongest pulse shaping effect in the SESAM (and thus the shortest pulses) to occur in resonance of the Fabry–Perot resonator, where however the losses are highest and thus the output power is in a minimum. We

conclude that the “good” operation points (with highest output power and shortest pulses) correspond to antiresonances of the Fabry–Perot resonator, although in these points the laser field hardly penetrates into the SESAM and hardly saturates the absorber. Although the general understanding is that significant absorber action is required to form short pulses, this is different in the concrete case due to the effect of spatial hole burning in the gain medium [29]. As this laser is operated far above the laser threshold (in order to suppress  $Q$ -switching instabilities), spatial hole burning is very strong. Experimentally this is apparent from the fact that even without a SESAM such lasers generate an output spectrum with a width comparable to the one obtained in mode-locked operation. While without this effect the spectral width of the laser output requires a balance between SESAM action and spectral narrowing in the gain medium, spatial hole burning alone can lead to a spectral width on the order of 0.3 nm. Thus, the SESAM then only has to phase-synchronize the longitudinal cavity modes, but is not required to stabilize their intensity pattern. Note that the phase synchronization becomes more difficult outside the antiresonance due to the dispersion of the Fabry–Perot cavity under these conditions.

Note that we have previously observed a similar behavior in a 77-GHz Nd:YVO<sub>4</sub> miniature laser where the rear flat crystal facet was also uncoated [18], [26]. At that time we interpreted these effects as resulting from dispersion generated in the Fabry–Perot resonator, acting together with the nonlinearity of the crystal to form soliton-like pulses. However, we found that the nonlinearity is actually too weak for soliton pulse shaping, as we later confirmed with numerical simulations.

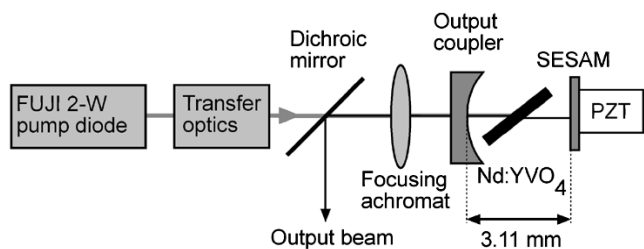


Fig. 3. Experimental setup of the 40-GHz laser with higher power. The pump and laser wavelengths are separated with a dichroic mirror. PZT stands for piezoelectric transducer.

We also did experiments using antireflection coated Nd:YVO<sub>4</sub> crystals, where the resonance effects are significantly weaker [25]. This, however, leads to roughly two times longer pulses. Also note that the shortest pulses from Nd:YVO<sub>4</sub> lasers have always been achieved with quasi-monolithic laser cavities, where spatial hole burning is strong, while lasers with a thin gain medium (not extending to the ends of the cavity) have always generated significantly longer pulses. Such a laser is also described in the following section.

### III. HIGH-POWER 40-GHz LASER

#### A. Concept and Previous State of the Art

By carefully optimizing a laser based on the presented quasi-monolithic design, it should be possible to reach a higher average output power. However, this would require a pump diode with higher power but not with lower brightness, because the mode area should not be increased by a larger factor than the intracavity power. It turns out that the currently available laser diodes with higher powers ( $> 0.5$  W) have a lower brightness and thus can not be used for a quasi-monolithic 40-GHz laser. A tapered amplifier could have the required brightness, but is more complex and expensive. For a given repetition rate, the demands on the pump brightness can be reduced by reducing the length of the pump-absorbing crystal, so that the pump beam divergence is less important. One possibility would be to use a quasi-monolithic design with a composite crystal that has a neodymium-doped section and an undoped section. However, we have used a design that is no longer quasi-monolithic: a Brewster-angled flat crystal of shorter length is placed between a SESAM and a curved output coupler (Fig. 3).

In 2002 we published a diode-pumped Nd:YVO<sub>4</sub> laser of this kind with a repetition rate of 10 GHz, an average output power of 2.1 W, and a pulse length of 14 ps [18]. This device was pumped with a 5-W diode that had an  $M^2$  of about 22 in both directions. Despite the high power, the brightness of this source is not suitable for a 40-GHz laser. In the following we describe a 40-GHz laser based on the same approach, but using a 2-W laser diode with higher brightness.

#### B. Experimental Setup

Fig. 3 shows a schematic of the complete laser setup. The pump source, provided by Fuji Photo Film Company, Ltd., is a 50- $\mu\text{m}$  stripe Al-free laser diode emitting up to 2 W of power at a wavelength of 807 nm for a mount temperature of 30°C. This device proved to be very reliable with more than 2000 h of

continuous operation at room temperature without degradation [30]. The beam quality factor is 12 for the slow axis and 2 for the fast axis. Two cylindrical lenses, an anamorphic prism pair and an achromatic lens with 30-mm focal length are used to focus the beam to a spot of  $24 \times 51 \mu\text{m}$  radius with 1.83 W in the crystal.

The laser cavity has a total physical length of 3.11 mm. The output coupler with a 3.8-mm radius of curvature has more than 90% transmission for the pump wavelength and a transmission of 0.25% at the laser wavelength. A crystal with 2% neodymium doping was chosen for maximum pump absorption without fracture or quenching effects at this power level. A pump absorption efficiency of roughly 50% is achieved with 0.5-mm crystal thickness. A longer crystal would allow for higher output power, but would increase the demands on the pump beam quality.

To avoid thermal quenching, the laser crystal was mounted on a copper block between indium foils. The SESAM is the same as used in the short pulse laser described in Section II.

#### C. Experimental Results

For 1.83 W of incident pump power on the crystal (0.8 W was absorbed), we obtain stable mode locking at a repetition rate of 40 GHz with 288 mW of average output power. The pulse energy was 7.2 pJ. Fig. 4 shows the radio frequency spectra from a fast photodiode, the optical spectrum and the autocorrelation. Although the autocorrelation trace shows some overlap of neighboring peaks, the 6.5-ps pulses at 40 GHz (corresponding to a period of 25 ps) are still well separated. The longer pulse duration compared to the laser of Section II can be explained by the fact that spatial hole burning has a weaker influence in this laser [29].

The saturation energy of the gain medium was independently calculated from the relaxation oscillations frequency and from the emission cross section of the Nd:YVO<sub>4</sub> crystal, and we obtained 6.8 and 4.5  $\mu\text{J}$ , respectively. The agreement is satisfactory since the mode size in the laser crystal and the total cavity losses are not precisely known.

#### D. Stability Versus Cavity Length

A somewhat unexpected observation is that the behavior of the laser changes periodically when the cavity length is changed. In general, the RF spectrum exhibits two lines rather than a single one; only for certain cavity lengths, which occur with a period of  $\approx 1 \mu\text{m}$ , do the two lines merge to a single one, and the autocorrelation shows the minimum width. The performance described above was obtained at these optimum points. This dependence on the cavity length is normally not observed in mode-locked lasers but was seen in an even stronger form in a similar laser with an antireflection coated crystal (with a smaller angle toward the beam) and in less clear form in the 10-GHz laser [18]. These effects are related to spurious intracavity reflections from the laser crystal. One can easily show that such reflections, even at a very low level of e.g.,  $10^{-8}$  of the power, can slightly modify the frequencies of the longitudinal cavity modes. These variations are periodic with the cavity length. Only for certain cavity lengths, occurring with a period of  $\approx 1 \mu\text{m}$  (assuming that the gain medium is near the middle of the cavity), are the frequencies equidistant,

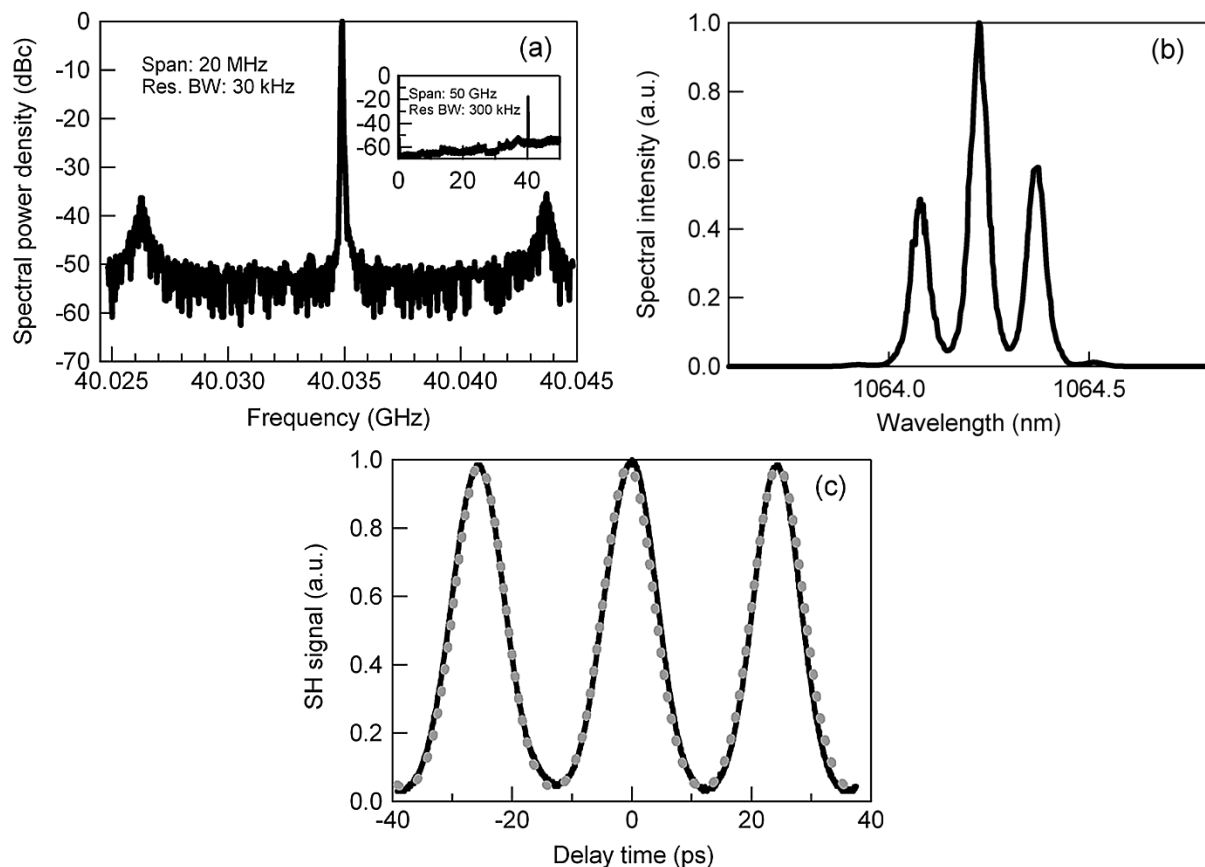


Fig. 4. (a) Radio frequency spectra of the 40-GHz high average output power laser. (b) Optical spectrum measured with 0.08 nm resolution bandwidth. The longitudinal modes with 40-GHz spacing are partly resolved. (c) Autocorrelation trace. The  $\text{sech}^2$  fit (dots) overlaps with the autocorrelation trace (line). The pulse length is 6.5 ps.

so that the SESAM can easily lock the phases of the modes for generation of short pulses. Indeed we have experimentally verified this variation of the mode frequencies with the cavity length, making our explanation of the observed periodicity highly plausible and consistent.

#### IV. CONCLUSION AND OUTLOOK

We have demonstrated two different diode-pumped Nd:YVO<sub>4</sub> lasers with 40-GHz repetition rate, which is the highest repetition rate demonstrated so far with passively mode-locked 1- $\mu\text{m}$  lasers. One laser was optimized for short pulses of 2.7-ps duration, while the other laser was optimized for a high output power of 288 mW.

We see some room for improvements with optimized SESAMs. A reduced saturation fluence would allow the realization of a higher repetition rate, or an increase in the modulation depth and thus a decrease in the pulse duration. In principle, this could also be achieved with stronger focusing on the absorber, but this could lead to overheating. A faster absorber recovery could be beneficial for high repetition rates. A factor of crucial importance is low nonsaturable losses, allowing low cavity losses, high slope efficiency, and leading to weaker heating.

Our discussion showed that high repetition rates from passively mode-locked lasers require a high pump brightness, because we need to operate far above threshold with a small

laser mode radius in the gain medium in order to suppress  $Q$ -switching instabilities. The following properties of the gain medium can help to reduce the demands on pump brightness: large laser cross sections, a high-amplification bandwidth (allow one to work with a SESAM with lower modulation depth), a high pump absorption (i.e., a high pump absorption cross section, a high absorption bandwidth, and a high doping density), and low parasitic losses. Good thermal properties are also important because they allow maximization of the doping level and thus the pump absorption. Compared to many other gain media, Nd:YVO<sub>4</sub> has excellent properties in these respects. Recently, some new gain materials of a similar kind, namely Nd:GdVO<sub>4</sub> [9], [31] and Nd:LuVO<sub>4</sub> [32], [33], have been shown to have even slightly superior properties and might therefore allow the performance levels of passively mode-locked 1- $\mu\text{m}$  laser to be raised somewhat further.

Laser diodes with higher powers tend to have a smaller brightness than low-power devices. For this reason, we are forced to use pump diodes with lower powers when constructing lasers with higher repetition rates, and the output powers get correspondingly smaller. Of course, the further development of high brightness pump diodes should help to improve the laser performance. Note that apart from the brightness, a small optical bandwidth is also important because it improves the pump absorption efficiency for small crystal lengths.

Passively mode-locked solid-state lasers can be used for pumping parametric oscillators (OPOs) in the multigigahertz

regime. At higher repetition rates, it becomes more difficult to achieve a high laser output power, while OPOs need even higher pump powers. Currently, optimized Nd:YVO<sub>4</sub> lasers can be used for direct OPO pumping up to a repetition rate of ≈10 GHz. For significantly higher repetition rate of e.g., 40 GHz, a pump laser with sufficient output power is not feasible with the currently available laser crystals and pump diodes, and it is then necessary to use an amplifier between laser and OPO [34].

## REFERENCES

- [1] U. Keller, "Recent developments in compact ultrafast lasers," *Nature*, vol. 424, pp. 831–838, 2003.
- [2] R. Ramaswami and K. Sivarajan, *Optical Networks: A Practical Perspective*. San Mateo, CA: Morgan Kaufmann, 1998.
- [3] D. A. B. Miller, "Optical Interconnects to Silicon," *IEEE J. Sel. Topics Quantum Electron.*, vol. 6, no. 6, pp. 1312–1317, Nov.–Dec. 2000.
- [4] K. J. Weingarten, M. J. W. Rodwell, and D. M. Bloom, "Picosecond optical sampling of GaAs integrated circuits," *IEEE J. Quantum Electron.*, vol. 24, no. 2, pp. 198–220, Feb. 1988.
- [5] A. Bartels, T. Dekorsky, and H. Kurz, "Femtosecond Ti:sapphire ring laser with 2-GHz repetition rate and its application in time-resolved spectroscopy," *Opt. Lett.*, vol. 24, pp. 996–998, 1999.
- [6] A. Hatziefremidis, D. N. Papadopoulos, D. Fraser, and H. Avramopoulos, "Laser sources for polarized electron beams in cw and pulsed accelerators," *Nucl. Instrum. Meth. A*, vol. 431, pp. 46–51, 1999.
- [7] S. Lecomte, L. Krainer, R. Paschotta, M. J. P. Dymott, K. J. Weingarten, and U. Keller, "Optical parametric oscillator with 10-GHz repetition rate and 100-mW average output power in the spectral region near 1.5 μm," *Opt. Lett.*, vol. 27, pp. 1714–1716, 2002.
- [8] S. Lecomte, R. Paschotta, M. Golling, D. Ebling, and U. Keller, "Synchronously pumped optical parametric oscillators in the 1.5-μm spectral region with a repetition rate of 10 GHz," *J. Opt. Soc. Amer. B*, vol. 21, pp. 844–850, 2004.
- [9] G. J. Spühler, S. Lecomte, M. Golling, R. Paschotta, D. Ebling, T. Ohgoh, T. Hayakawa, K. J. Weingarten, and U. Keller, "Compact 10-GHz Nd:GdVO<sub>4</sub> laser with 0.5-W average output power and low timing jitter," *Opt. Lett.*, vol. 29, pp. 2629–2631, 2004.
- [10] E. Yoshida and M. Nakazawa, "80–200 GHz erbium doped fiber laser using a rational harmonic mode-locking technique," *Electron. Lett.*, vol. 32, pp. 1370–1372, 1996.
- [11] S. Arahira, Y. Matsui, and Y. Ogawa, "Mode-locking at very high repetition rates more than terahertz in passively mode-locked distributed-Bragg-reflector laser diodes," *IEEE J. Quantum Electron.*, vol. 32, no. 7, pp. 1211–1224, Jul. 1996.
- [12] U. Keller, D. A. B. Miller, G. D. Boyd, T. H. Chiu, J. F. Ferguson, and M. T. Asom, "Solid-state low-loss intracavity saturable absorber for Nd:YLF lasers: An antiresonant semiconductor Fabry–Perot saturable absorber," *Opt. Lett.*, vol. 17, pp. 505–507, 1992.
- [13] U. Keller, K. J. Weingarten, F. X. Kärtner, D. Kopf, B. Braun, I. D. Jung, R. Fluck, C. Hönninger, N. Matuschek, and J. Aus der Au, "Semiconductor saturable absorber mirrors (SESAMs) for femtosecond to nanosecond pulse generation in solid-state lasers," *IEEE J. Sel. Topics Quantum Electron.*, vol. 2, no. 3, pp. 435–453, Sep. 1996.
- [14] R. Häring, R. Paschotta, A. Aschwanden, E. Gini, F. Morier-Genoud, and U. Keller, "High-Power passively mode-locked semiconductor lasers," *IEEE J. Quantum Electron.*, vol. 38, no. 9, pp. 1268–1275, Sep. 2002.
- [15] S. Hoogland, S. Dhanjal, A. C. Tropper, S. J. Roberts, R. Häring, R. Paschotta, and U. Keller, "Passively mode-locked diode-pumped surface-emitting semiconductor laser," *IEEE Photon. Technol. Lett.*, vol. 12, no. 9, pp. 1135–1137, Sep. 2000.
- [16] A. Garnache, S. Hoogland, A. C. Tropper, I. Sagnes, G. Saint-Girons, and J. S. Roberts, "<500-fs soliton pulse in a passively mode-locked broadband surface-emitting laser with 100-mW average power," *Appl. Phys. Lett.*, vol. 80, pp. 3892–3894, 2002.
- [17] A. Aschwanden, D. Lorenser, H. J. Unold, R. Paschotta, E. Gini, and U. Keller, "10-GHz passively mode-locked surface-emitting semiconductor laser with 1.4 W output power," presented at the Conf. Lasers and Electro-Optics (CLEO), (OSA), Postdeadline CPDB8, 2004.
- [18] L. Krainer, R. Paschotta, S. Lecomte, M. Moser, K. J. Weingarten, and U. Keller, "Compact Nd:YVO<sub>4</sub> lasers with pulse repetition rates up to 160 GHz," *IEEE J. Quantum Electron.*, vol. 38, no. 10, pp. 1331–1338, Oct. 2002.
- [19] L. Krainer, R. Paschotta, J. Aus der Au, C. Hönninger, U. Keller, M. Moser, D. Kopf, and K. J. Weingarten, "Passively mode-locked Nd:YVO<sub>4</sub> laser with up to 13 GHz repetition rate," *Appl. Phys. B*, vol. 69, pp. 245–247, 1999.
- [20] S. C. Zeller, L. Krainer, G. J. Spühler, R. Paschotta, M. Golling, D. Ebling, K. J. Weingarten, and U. Keller, "Passively mode-locked 50-GHz Er:Yb:glass laser," *Electron. Lett.*, vol. 40, pp. 875–876, 2004.
- [21] K. J. Weingarten, D. C. Shannon, R. W. Wallace, and U. Keller, "Two gigahertz repetition rate, diode-pumped, mode-locked, Nd:yttrium lithium fluoride (YLF) laser," *Opt. Lett.*, vol. 15, pp. 962–964, 1990.
- [22] K. J. Weingarten, A. A. Godil, and M. Gifford, "FM modelocking at 2.85 GHz using a microwave resonant optical modulator," *IEEE Photon. Technol. Lett.*, vol. 4, no. 10, pp. 1106–1109, Oct. 1992.
- [23] P. A. Schulz and S. R. Henion, "5-GHz mode locking of a Nd:YLF laser," *Opt. Lett.*, vol. 16, pp. 1502–1504, 1991.
- [24] A. A. Godil, A. S. Hou, B. A. Auld, and D. M. Bloom, "Harmonic mode locking of a Nd:BEL laser using a 20-GHz dielectric resonator/optical modulator," *Opt. Lett.*, vol. 16, pp. 1765–1767, 1991.
- [25] L. Krainer, R. Paschotta, M. Moser, and U. Keller, "Passively mode-locked picosecond lasers with up to 59 GHz repetition rate," *Appl. Phys. Lett.*, vol. 77, pp. 2104–2105, 2000.
- [26] L. Krainer, R. Paschotta, M. Moser, and U. Keller, "77 GHz soliton modelocked Nd:YVO<sub>4</sub> laser," *Electron. Lett.*, vol. 36, pp. 1846–1848, 2000.
- [27] C. Hönninger, R. Paschotta, F. Morier-Genoud, M. Moser, and U. Keller, "Q-switching stability limits of continuous-wave passive mode locking," *J. Opt. Soc. Am. B*, vol. 16, pp. 46–56, 1999.
- [28] A. Oosenbrug, "Reliability aspects of 980-nm pump lasers in EDFA applications," *Proc. SPIE*, vol. 3284, pp. 20–27, 1998.
- [29] B. Braun, K. J. Weingarten, F. X. Kärtner, and U. Keller, "Continuous-wave mode-locked solid-state lasers with enhanced spatial hole-burning, Part I: Experiments," *Appl. Phys. B*, vol. 61, pp. 429–437, 1995.
- [30] F. Yamanaka, M. Wada, T. Kuniyasu, T. Ohgoh, T. Fukunaga, and T. Hayakawa, "2 W reliable operation in 50 μm-wide InGaAsP/InGaP/AlGaAs (λ = 810 nm) SQW diode lasers with tensile-strained InGaP barriers," *Electron. Lett.*, vol. 37, pp. 1289–1290, 2001.
- [31] B. Zhang, L. Gang, M. Chen, Z. Zhang, and Y. Wang, "Passive mode locking of a diode-end-pumped Nd:GdVO<sub>4</sub> laser with a semiconductor saturable absorber mirror," *Opt. Lett.*, vol. 28, pp. 1829–1831, 2003.
- [32] C. Maunier, J.-L. Doualan, R. Moncorge, A. Speghini, M. Bettinelli, and E. Cavalli, "Growth, spectroscopic characterization, and laser performance of Nd:LuVO<sub>4</sub>, a new infrared laser material that is suitable for diode pumping," *J. Opt. Soc. Amer. B*, vol. 19, pp. 1794–1800, 2002.
- [33] J. Liu, H. Zhang, Z. Wang, J. Wang, Z. Shao, M. Jiang, and H. Weber, "Continuous-wave and pulsed laser performance of Nd:LuVO<sub>4</sub> crystal," *Opt. Lett.*, vol. 29, pp. 168–170, 2004.
- [34] S. Lecomte, R. Paschotta, S. Pawlik, B. Schmidt, K. Furusawa, A. Malinowski, D. J. Richardson, and U. Keller, "39-GHz repetition rate optical parametric oscillator in the 1.5-μm spectral region," *Opt. Lett.*, to be published.



**Steve Lecomte** was born in Neuchâtel, Switzerland, in 1974. He received the Diploma degree in physics from the University of Neuchâtel, Neuchâtel, Switzerland, in 1998. He is currently working toward the Ph.D. degree at the Ultrafast Laser Physics Laboratory, Swiss Federal Institute of Technology (ETH), Zürich, Switzerland.

From 1999 to 2001, he was with the Nonlinear Optics Laboratory, ETH, Switzerland, where he conducted research on polymer waveguides and third-order nonlinearities in organic molecules and polymers. In 2001, he joined the Ultrafast Laser Physics Laboratory, where he is researching high-repetition-rate all-solid-state lasers and high-repetition-rate optical parametric oscillators.

Mr. Lecomte is a student member of the Optical Society of America.



Swiss Federal Institute of Technology (ETH), Zurich, Switzerland.

**Markus Kalisch** was born in Hamburg, Germany, in 1977. He received the Diploma degree in experimental physics from the Swiss Federal Institute of Technology (ETH), Zurich, Switzerland, in 2003. He received a scholarship from the German Academic Exchange Office to study for the M.Sc. degree in applied mathematics at the University of Oxford, England, which he received in 2004, and at which occasion he was awarded the Gutierrez Toscano Prize. He is currently working toward the Ph.D. degree at the Department of Mathematics at the

**Lukas Krainer** was born in Hohenems, Austria, in 1974. He received the Diploma and Ph.D. degrees in experimental physics from the Swiss Federal Institute of Technology (ETH), Zürich, Switzerland, in 1997 and 2002, respectively.

In 1998, he joined the Institute of Quantum Electronics, ETH. In 2002, he joined GigaTera Inc. In 2003, he returned to the Institute of Quantum Electronics, ETH, where his research focuses on passively mode-locked high-repetition-rate all-solid-state laser sources.

Dr. Krainer is a member of the Optical Society of America.

**Gabriel J. Spühler** was born in Zürich, Switzerland, in 1972. He received the Diploma and Ph.D. degrees in physics in 1996 and 2000, respectively, from the Swiss Federal Institute of Technology (ETH), Zürich, Switzerland.

In 2001, he joined GigaTera Inc. in Zürich, Switzerland, a start-up company in the field of telecommunications, where he worked on the development and commercialization of compact solid-state lasers with ultrahigh repetition rates. In 2003 he also joined the Swiss Federal Institute of Technology (ETH) as a Postdoctoral Associate, where he currently works on diode-pumped passively mode-locked solid-state lasers.

Dr. Spühler is a member of the Optical Society of America.



**Rüdiger Paschotta** was born in Tailfingen, Germany, in 1965. In 1994, he received the Ph.D. degree in physics from the University of Konstanz, Konstanz, Germany, in quantum optics and nonlinear optics.

From 1994 to 1997, he worked on various aspects of fiber lasers and fiber amplifiers as a Postdoctoral Researcher in the group of A. Töpfer and D. C. Hanna at the Optoelectronics Research Centre, University of Southampton, Southampton, U.K. In 1997, he moved to the University of Paderborn, Paderborn, Germany, to work in nonlinear optics and integrated optics. Since November 1997, he has been conducting research on mode-locked lasers in the group of U. Keller at the Swiss Federal Institute of Technology (ETH), Zürich, Switzerland. In June 2004, he founded the company RP Photonics Consulting GmbH while continuing to do research at ETH part time. His scientific interests are currently focused on the physics of passive mode locking, optimization of mode-locked lasers for high-output powers or high pulse repetition rates, the development of mode-locked high-power surface-emitting semiconductor lasers, high-power nonlinear frequency conversion, and noise in optics.



**Matthias Golling** was born in Sulz/Neckar, Germany, in 1971. He received the Dipl.-Ing. and Dr.-Ing. degrees in electrical engineering from the University of Ulm, Ulm, Germany, in 1997 and 2004, respectively.

In 1996, he was with NTT Optoelectronic Labs., Ibaraki, Japan, investigating erbium-doped waveguides. He is now with the Institute of Quantum Electronics, Swiss Federal Institute of Technology, Zurich, Switzerland. His research interests are focused on the crystal growth of high-speed electronic and optoelectronic devices with molecular beam epitaxy.



**Dirk Ebling** received the M.Sc. and Ph.D. degrees in chemistry from the University of Duesseldorf, Germany. His thesis research concerned the fabrication of submicron structures in alumina and their electrical and optical properties.

After graduation in 1991, his research focused on the characterization and growth of compound semiconductor materials at the University of Freiburg, Germany. Beside the development of X-ray radiation detectors, his research was focused on the development of advanced ultraviolet sensors from wide bandgap materials and on the MBE growth and analysis of group V alloys in III-V semiconductors. Since 2001 he has been involved in the growth and development of optical devices from III/V materials for laser applications at the FIRST Center for Micro- and Nanosciences, Swiss Federal Institute of Technology (ETH), Zürich, Switzerland.



**Tsuyoshi Ohgoh** was born in Tokyo, Japan, in 1969. He received the B.S. and M.E. degrees in electrical engineering from Tokyo University of Agriculture and Technology, Tokyo, Japan, in 1992 and 1994, respectively.

He joined Fuji Photo Film Company, Ltd., in 1994 and is now a Researcher in the Advance Core Technology Laboratories, Kanagawa, Japan. He has been engaged in the research and development of semiconductor lasers, especially in 0.8-mm Al-free high-power lasers.

Mr. Ohgoh is a member of the Japan Society of Applied Physics.



**Toshiro Hayakawa** (M'81-SM'93) was born in Nagoya, Japan, in 1953. He received the B.E. and M.E. degrees in electrical engineering and the Dr.E. degree in electronics engineering from Kyoto University, Kyoto, Japan, in 1976, 1978, and 1984, respectively.

From 1978 to 1988, he was with Sharp Corporation, where he engaged in the first reliable AlGaAs laser diodes emitting at 780 nm, which made it possible to commercialize the compact disk player in 1982. This laser became the first commercial laser diode mass produced. He developed various lasers for optical recording and the first reliable 740-nm lasers. Since 1982, he has been engaged in many types of modulated semiconductor structures using MBE. He successfully prepared (111)-oriented GaAs-AlGaAs quantum wells and quantum-well laser diodes. This opened the new area of orientation-dependent quantum size effects and became a landmark of high-index plane growth of quantum structures. This laser emitted a high-power of 3.7 W continuous wave from single 100- $\mu$ m aperture. In addition, he successfully prepared AlGaInP red laser diodes with solid source molecular beam epitaxy (MBE) using red phosphorus. This is now being used for mass production of DVD lasers. From 1988 to 1993, he was with Eastman Kodak (Japan) Ltd., where he worked on the establishment of the new Research and Development Center and lead a group for MBE and laser diode research and development as a project leader. He has developed the production-quality MBE technology for high-power AlGaAs laser diodes. He also has developed InGaAs strained layer quantum-well lasers with improved temperature sensitivity by using short-period superlattice barrier layers. In 1993, he joined Fuji Photo Film Company, Ltd. Since then, he has developed and commercialized Al-free active-region high-power laser diodes using metal-organic chemical vapor deposition (MOCVD), which have been used as excitation sources of blue and green SHG lasers in the first laser photography printer. He has developed the first reliable 1060-nm lasers with highly strained InGaAs single quantum wells. He is currently responsible for the research and development of a variety of materials and devices as a Divisional Manager at Advanced Core Technology Laboratories, Kanagawa, Japan. He has published more than 50 technical papers and holds over 50 U.S. patents.

Dr. Hayakawa is a member of the Japan Society of Applied Physics, the Institute of Electronics, Information and Communication Engineers, and the Institute of Electrical Engineers of Japan. He was a corecipient of Invention Prize from Japan Institute of Invention and Innovation in 1987.



**Susanne Pawlik** was born in Paderborn, Germany, in 1968. She received the diploma degree in physics from the University of Paderborn, Germany, and the Dr. sc. nat. degree from the Swiss Federal Institute of Technology (ETH), Zürich, Switzerland, in 1993 and 1998, respectively.

In 1998, she joined Vivastar AG, Switzerland, where she worked on the development and production of optical-storage media. In 1999, she joined the R&D department of JDS Uniphase, today's Bookham Inc. site in Zurich, Switzerland, where she is currently involved with the development of GaAs-based high-power semiconductor laser diodes for telecom and industrial applications.

**Berthold Schmidt** (M'99) was born in Würzburg, Germany, in 1968. He received the M.Sc. degree in physics from the State University of New York at Albany, and the Diploma degree from the Julius-Maximilian University of Würzburg, Germany, in 1991 and 1994, respectively. In 1999, he received the Dr. rer. nat. degree in physics from the Technical University Munich, Germany.

From 1995 to 1998, he was an Associated Employee in the department for corporate research and development of the Siemens AG, Munich, Germany. His research interest was focused on the improvement of wavelength tunable InAsP-InP laser diodes and other optoelectronic devices. From December 1998 to 2000, he was with JDS Uniphase as a Project Leader for the development of GaAs-based pump laser diodes. Since the end of 2000, he has been a manager for "Advanced Devices" first at Nortel Networks and, since 2002, at Bookham. In this position, he is responsible for the development and qualification of high-power semiconductor laser products for telecom and industrial applications. He has authored or coauthored more than 30 articles on semiconductor optoelectronics in scientific journals, conference proceedings, and books.

Dr. Schmidt is member of the DPG and SPIE, and a Board Member of the Swiss Society for Optics and Microscopy (SSOM).



**Ursula Keller** (M'89-SM'01) as born in Zug, Switzerland, in 1959. She received the Diploma degree in physics from the Federal Institute of Technology (ETH) Zürich, Switzerland, in 1984. From late 1984 to 1985 she worked on optical bistability at Heriot-Watt University, Edinburgh, U.K. She then moved to Stanford University, Stanford, CA and received the M.S. and Ph.D. degrees in applied physics in 1987 and 1989, respectively. For her first year at Stanford, she held a Fulbright Fellowship and the following year she was an IBM Predoctoral

Fellow. Her Ph.D. research was in optical probing of charge and voltage in GaAs integrated circuits and in low-noise ultrafast laser systems.

In 1989, she became a Member of Technical Staff (MTS) at AT&T Bell Laboratories, Holmdel, NJ, where she conducted research on photonic switching, ultrafast laser systems, and semiconductor spectroscopy. In March 1993, she was appointed an Associate Professor and in October 1997, she became a Full Professor in the Physics Department at ETH. Her current research interests are in ultrafast lasers, attosecond science, ultrafast spectroscopy, and novel devices for applications in optical information processing and communication. She has published more than 200 peer-reviewed journal papers, 7 book chapters, and holds or has applied for 16 patents.

In 1998, Prof. Keller received the Carl Zeiss Research Award and in 2004 the first Berthold Leibinger Innovation Prize for her pioneering work in novel mode-locking and *Q*-switching techniques using semiconductor saturable absorber mirrors (SESAMs). In 2000, she was elected for the LEOS Distinguished Lecturer Award for mode-locked solid-state lasers. In 2003, she became an OSA Fellow for pioneering contributions to the generation of few-optical-cycle laser pulses and applications and the development of semiconductor saturable absorber mirrors. She is an elected foreign member of the Royal Swedish Academy of Sciences, a fellow of the Optical Society of America (OSA), a member of the European Physical Society (EPS), the Swiss Physical Society (SPS), and the Swiss Academy of Technical Sciences (SATW).